

NIGERIAN JOURNAL OF
TECHNOLOGY



VOLUME 36, NUMBER 2, APRIL 2017



UNIVERSITY OF NIGERIA PRESS LTD

PRINT ISSN:0331-8443
ELECTRONIC ISSN: 2467-8821

 **tetfund**
TERTIARY EDUCATION TRUST FUND
TETFUND SUPPORTED
TETFUND/UNI/NSUKKA/ARJ/1

Nigerian Journal of Technology

p-ISSN: 0331-8443 e-ISSN: 2467-8821

EDITOR-IN-CHIEF

Engr. Prof. J. C. Agunwamba
jonah.agunwamba@unn.edu.ng
Department of Civil Engineering,
University of Nigeria, Nsukka, NIGERIA

EDITOR & JOURNAL MANAGER

Engr. Prof. E. S. Obe
+234-812-323-1094
Department of Electrical Engineering,
University of Nigeria, Nsukka, NIGERIA

Editorial Assistants: IFEOMA GOODNESS UGWU and TITUS CHINEDU OBE

ASSOCIATE (SECTION) EDITORS

SECTION A
Prof. FO Okafor,
Prof. OS Abejide

SECTION B
Prof. DON Obikwelu
Dr. IC Ezema

SECTION C
Prof. LU Anih
Dr. ON Iloanusi

SECTION D
Prof. CC Mbajirogu
Dr. BO Ugwuishiwu

EDITORIAL BOARD

- Prof. OV Ekechukwu, National Universities Commission, Abuja, NIGERIA
Dr. S. Jijajitsawat, Department of Transportation Engineering, Naresuan University, THAILAND
Dr. SFM Karugaba, Department of Electrical Engineering, Dar-es-Salaam Institute of Technology, Tanzania
Prof. AO Ekwue, Sinclair Knight Merz (Europe) Ltd/Institute of Power Systems, Brunel University, UNITED KINGDOM
Prof. S. Hloch, Department of Manufacturing Management, Technical University of Košice, SLOVAKIA
Prof. K. Nadolny, Department of Production Engineering, Koszalin University of Technology, POLAND
Prof. W. Kapłonek, Subject Group of Metrology and Quality, Koszalin University of Technology, POLAND
Dr. Ajita Rattani, Department of Mechanical Engineering, University of Cagliari, Cagliari, ITALY
Prof. JO Ojo, Center for Energy Systems Research, Tennessee Technological University, Cookeville, USA
Prof. A Binder, Institute for Electrical Energy Conversion, Technical University, Darmstadt, GERMANY
Prof. A Muetze, Electrical Power Engineering, Technical University, Graz, AUSTRIA
Prof. MO Omoigui, Engineering Power Electronics, Obafemi Awolowo University Ife, NIGERIA
Prof. OU Oparaku, Department of Electronic Engineering, University of Nigeria, Nsukka, NIGERIA
Prof. DON Obikwelu, Department of Materials and Metallurgical Engineering, University of Nigeria, Nsukka, NIGERIA
Dr. Sosthenes Karugaba, Department of Computer Engineering, Tennessee Technological University, Cookeville, Tennessee, USA
Prof. T. Senjyu, Department of Electrical Engineering, University of the Ryukyus, Nishihara, Okinawa, JAPAN
Prof. ARKennedy, Department of Mechanical, Materials and Manufacturing Engineering, University of Nottingham, UK.
Dr. A. Rinanti, Jl. Pendidikan No. 17, RT07/RW 09, Cilandak Barat, Jakarta Selatan 12430, INDONESIA
Dr. C. A. Chidolue, Department of Civil Engineering, Nnamdi Azikiwe University, Awka, Anambra State, NIGERIA
Dr. R. Ehigiator, Department of Geomatics, Faculty of Environmental Sciences, University of Benin, Edo State, NIGERIA
Prof. T. C. Madueme, Department of Electrical Engineering, University of Nigeria Nsukka, Enugu State, NIGERIA
Prof. OCizinyon, Department of Civil Engineering, University of Benin, NIGERIA
Prof. FORumwense, Department of Mechanical Engineering, University of Benin, NIGERIA
Dr. RK Ajao, Department of Water Resources Engineering, University of Ilorin, NIGERIA
Prof. G. Chukwudebe, Federal University of Technology, Owerri, NIGERIA
Prof. AP Onwualu, Raw Materials Research and Development Council, Maitam Abuja, NIGERIA
Prof. S. I. Neife, Department of Metallurgical and Materials Engineering, University of Ndifu-Alike Ikwo, Ebonyi State, Nigeria.
Prof. EC Ejiogu, Department of Electrical Engineering, Ritsumeikan University, Kusatsu-City, JAPAN
Dr. J. Enokela, Department of Electrical Engineering, University of Agriculture, Makurdi, NIGERIA
Prof. SN Ndubisi, Department of Electrical Engineering, University of Port Harcourt, NIGERIA
Dr. AW Salami, Department of Civil Engineering, University of Ilorin, NIGERIA
Prof. JA Otun, Department of Civil Engineering, Ahmadu Bello University, Zaria, NIGERIA
Prof. Idris Abubakar, Department of Civil Engineering, Ahmadu Bello University, Zaria, Zaria, Kaduna State, Nigeria.
Prof. CC Mbajirogu, Department of Agric and Bioresources Engineering, University of Nigeria, Nsukka, NIGERIA
Prof. CI Ani, Department of Electronic Engineering, University of Nigeria, Nsukka, NIGERIA
Prof. HAP Audu, Department of Civil Engineering, University Benin, Benin City Edo State, NIGERIA
Prof. AC Igboanugo, Department of Production Engineering, University of Benin, NIGERIA
Prof. SO Enibe, Department of Mechanical Engineering, University of Nigeria, Nsukka, NIGERIA
Dr. O. Kamdoun, Université de Ngaoundéré, Faculté des Sciences, Département de Chimie, B.P 454, Ngaoundéré, CAMEROUN
Prof. O. S. Abejide, Department of Civil Engineering, Ahmadu Bello University, Zaria, Zaria, Kaduna State, NIGERIA
Dr. S. R. Tchamango, Université de Ngaoundéré, Faculté des Sciences, Département de Chimie, B.P 454, Ngaoundéré, CAMEROUN
Dr. V. Aigbodion, Department of Materials and Metallurgical Engineering, University of Nigeria, Nsukka, Enugu State, NIGERIA

FOUNDING EDITORIAL BOARD (between 1975 and 1982)

- | | | | |
|-------------------------------|------------------------------------|--------------------------|---------------------------|
| Engr. Prof. LA Agu (late) | Engr. Prof. N Egbuniwe (late) | Engr. Prof. CC Ezekwe | Engr. Prof. OC Iloeje |
| Engr. Prof. RM Madu (late) | Engr. Prof. OJ Eze-Uzoamaka (late) | Engr. Prof. AN Nzeako | Engr. Prof. GA Makanjuola |
| Engr. Prof. CC Ezeilo | Engr. Prof. SC Chikwendu | Engr. Prof. EU Odigboh | Engr. Prof. SO Onyegegbu |
| Engr. Prof. MU Agu | Engr. Prof. MO Chijioke | Engr. Prof. DC Onyejekwe | Engr. Prof. CO Akubue |
| Engr. Prof. NN Osadebe (late) | Engr. Prof. M. A. Nwachukwu (late) | Engr. Prof. CC Osuagwu | |

COST PER COPY (All costs exclude postage)

Individual – NIGERIA = ₦2000; Institution – NIGERIA = ₦4000
Individual – FOREIGN = \$20; Institution – FOREIGN = \$40

© Faculty of Engineering, University of Nigeria, Nsukka, Nigeria, 2016

www.nijotech.com nijo.tech@unn.edu.ng

Bank: Diamond Bank PLC. Account Name: NIGERIAN JOURNAL OF TECHNOLOGY. Account Number: 0019429431. Sort Code: 063251139. The swift code for international transfers is: DBLNGLAXXX

Nigerian Journal of Technology

VOLUME 36, NUMBER 2, APRIL 2017

... publishing original technical and scholarly reports since 1975

www.nijotech.com

nijo.tech@unn.edu.ng

TABLE OF CONTENTS

SECTION A: BUILDING, CIVIL & GEOTECHNICAL ENGINEERING

Determination of Verticality of Reservoir Engineering Structure from Laser Scanner Data	R. Ehigiator-Irughe and M. O. Ehigiator	322
Structural Behavior of Metakaolin Infused Concrete Structure	J. O. Akinyele, S. O. Odunfa, A. A. Famoye and S. I. Kuye	331
Compaction and Consolidation Characteristics of Lateritic Soil of a Selected Site in Ikole Ekiti, Southwest Nigeria	A. Bolarinwa, J.B. Adeyeri and T. C. Okeke	339
Equilibrium Approach in the Derivation of Differential Equations for Homogeneous Isotropic Mindlin Plates	C. C. Ike	346
Kantorovich-Euler Lagrange-Galerkin's Method for Bending Analysis of Thin Plates	C. C. Ike	351
Solution of Free Harmonic Vibration Equation of Simply Supported Kirchhoff Plate by Galerkin-Vlasov Method	B. O. Mama, H. N. Onah, C. C. Ike and N. N. Osadebe	361
Models for Predicting Compressive Strength and Water Absorption of Laterite-Quarry Dust Cement Block using Mixture Experiment	F. O. Okafor and E. A. Egbe	366
Modified Water-Cement Ratio Law for Compressive Strength of Rice Husk Ash Concrete	M. Abdullahi, G. O. Ojelade and S. M. Auta	373
Experimental Validation of Optimum Resistance Moment of Concrete Slabs Reinforced With Carbon Fibre-Reinforced Plastic	E. E. Okoro, A. U. Nwafor and O. S. Abejide	380
Utilisation of Rice Husk Ash for Improvement of Deficient Soils in Nigeria: A Review	M. Alhassan and M. M. Alhaji	386
Evaluation of Land Surface Temperature Parameterization Approaches using Surface- Layer Observations	R.T. Akinnubi, and M. O. Adeniyi.	395
Performance of Concrete with Partial Replacement of Fine Aggregates with Crushed Waste Glass	A. W. Otunyo and B. N. Okechukwu	403

SECTION B: CHEMICAL, INDUSTRIAL, MATERIALS, MECHANICAL, METALLURGICAL, PETROLEUM & PRODUCTION ENGINEERING

Finite Element Analysis of Plastic Recycling Machine Designed for Production of Thin Filament Coil	P. K. Farayibi	411
Assessment of Some Mechanical Properties and Microstructure of Particulate Periwinkle Shell-Aluminium 6063 Metal Matrix Composite (PPS-ALMMC) Produced by Two-Step Casting	R. Umunakwe, D. J. Olaleye, A. Oyetunji, O. C. Okoye and I. J. Umunakwe	421



MODIFIED WATER-CEMENT RATIO LAW FOR COMPRESSIVE STRENGTH OF RICE HUSK ASH CONCRETE

M. Abdullahi^{1*}, G. O. Ojelade², and S. M. Auta³

^{1,3} CIVIL ENGINEERING DEPARTMENT, FEDERAL UNIVERSITY OF TECHNOLOGY, MINNA, NIGER STATE, NIGERIA

² FEDERAL MINISTRY OF LABOUR AND PRODUCTIVITY, CARDINAL OLU BUNMI OKOGIE STREET, IKOYI LAGOS, LAGOS STATE, NIGERIA.

*E-mail addresses:*¹abdulapai@yahoo.com,²daddyk67@yahoo.com,³samuel.auta@futminna.edu.ng

ABSTRACT

This work examines the modification of age long water – cement ratio law of Ordinary Portland Cement (OPC) concrete to cater for concrete with Rice Husk Ash (RHA). Chemical analysis of RHA produced under controlled temperature of 600°C was carried out. A total of one hundred and fifty (150) RHA concrete cubes at five different water/binder ratios and at six replacement levels of RHA (5%, 10%, 15%, 20%, 25%, 30%) were produced with specific attention given to cement/water (c/w) content and RHA/water (r/w) content. The cubes were subjected to compressive strength test at 56 days of curing producing a compressive strength in the range of 3.77 N/mm² to 34.04N/mm². A linear polynomial model was fitted into the experimental data using Minitab Package and was found adequate with an adjusted coefficient of determination of 73.0%. Test results show that the compressive strength of hardened RHA concrete depends on cement/water content by weight on one part and RHA/water content by weight on the other part. This indicates that the model equation is suitable to evaluate the compressive strength of RHA concrete at 95% confidence interval and the linear model has the capability of explaining the variability in the data by 73%.

Keywords: water-cement ratio, compressive strength, rice husk ash, model.

1. INTRODUCTION

Concrete is the most widely used construction material for various types of structures due to its structural stability and strength [1]. It has attained the status of a major building material in modern construction technology. Concrete is the best material of choice where strength, durability, imperviousness, fire resistance and absorption resistance are required. It is a composite material that could be used solely or possibly with other materials depending on the design, quality requirement and cost of construction.

The most common form of concrete nowadays consists of water, cement, and fine aggregate and coarse aggregate. Cement and water form a paste that coat particles of fine and coarse aggregate, hardens and gain strength through a chemical reaction called hydration. A properly designed concrete mix will possess the desired workability for fresh concrete and the required durability and strength for the hardened concrete. The widely used cement is Ordinary Portland Cement (OPC). Concrete is brittle and weak in tension but its compressive strength is about ten to thirteen times greater than its tensile strength [2]. However Mosley and Bungey [3] found the compressive strength to be about eight times greater than the tensile strength.

The most costly input into the production of concrete is cement. Rao et al [1] opined that in the milling of paddy, about

78% of the weight is received as rice, broken rice and bran, the rest 22% is received as husk. The husk of rice is generally considered as a waste product and this over 20% by weight of rice is quite large and thus constitutes environmental nuisance. Several research efforts have been made to utilise waste materials in construction works [4, 5, 6]. Burnt Rice Husk (RH) produces Rice Husk Ash (RHA). Small quantity of RHA has been used as pozzolans with some degree of successes [7]. Apart from successful usage of small quantity of RHA without sacrificing the strength of mortar, it was noted that proper consumption of RHA contributes in solving environmental pollution [8]. Rice husk ash (RHA) is generated by burning rice husk; on burning, cellulose and lignin are removed leaving behind silica ash. For amorphous silica the burning temperature should be from 500 to 700°C [9]. Partial replacement of cement with RHA will greatly assist in reducing the carbon dioxide emission into the environment, reduce the solid agricultural waste (rice husk) and also produce more sustainable cheaper concrete products.

To this end, studies on the development of modified water-cement ratio law for concrete incorporating RHA is timely and justifiable. The relationship between the compressive strength and the cement-water ratio is approximately linear in the range of cement-water ratios between about 1.2 and 2.5. The compressive strength is therefore directly proportional to

* Corresponding author tel: +234 – 816 – 741 – 5678

cement-water ratio [9]. In other words, the compressive strength increases with a decrease in water-cement ratio. High value of water-cement ratio results in greater pore spaces in the hardened concrete leading to lower compressive strength. This is possible since normal concrete fails mainly within the mortar phase.

1.1 Development of Water/Cement Ratio Law

Abram found out that for a full compaction at a given age and normal temperature, the strength of concrete is inversely related to the water- cement ratio [9]. This rule was found to fit into the relation

$$S = \frac{A_0}{B_0^x} \tag{1}$$

Where S is the strength of concrete (N/mm²), A₀ and B₀ are empirical constant and x is the water/cement ratio.

Popovics (1998) provided values for A₀ and B₀ such that B₀>1, A₀ = 96.5266MPa. However if OPC and Pozzolans [10] are to be used, then the "cement" in water- cement ratio changes to "binder" so that it is now termed water/ binder ratio. For this purpose, Hedegaard and Hansen [11] had earlier considered the modification of Abram's law to suit replacement of cement with fly ash (FA). They started with Bolomeys equation which was based purely on empirical basis but also similar to Abram's law. The equation is given as:

$$S = A \frac{c}{w} + E \tag{2}$$

Where S is the Strength of concrete, c is the Cement content, w is the Water content of concrete, and A and E are constants for given material, age and curing condition of concrete.

Hedegaard and Hansen [11] observed that during hydration of Portland cement in concrete, crystalline calcium hydroxide is formed as well as cement gel. However this calcium hydroxide will react with fly ash a pozzolans in concrete to produce a colloidal gel similar in structure and properties to the gel formed when Portland cement hydrates. It therefore suggest that the strength development of Portland Cement when FA is added is due to the pore - filling mechanism caused by hydration of Portland cement plus the pore - filling mechanism caused by reaction between FA, water and the calcium hydroxide. Hedegaard and Hansen [11] therefore presented the relation

$$S = A \frac{c}{w} + B \frac{f}{w} + E \tag{3}$$

In (3), S is the Compressive strength of concrete (N/mm²), c is the Cement content in the concrete f is the Fly ash content in the concrete, w=Water content in the concrete and A, B, and E are constant for given material, age and curing condition of concrete. Premise on Hedegaard and Hansen [11] observation, this paper seeks to provided response of equation (3), by using rice husk ash as a substitute for fly ash. Thus the target equation is:

$$f_{cu} = A \frac{c}{w} + B \frac{r}{w} + E \tag{4}$$

Where f_{cu} = S = Compressive strength of concrete. r is the rice husk ash and other parameters are as defined in (3).

2. MATERIALS AND METHODS

2.1 Material

The materials used for this work are rice husk, cement, fine aggregate, coarse aggregate, water. For the purpose of this work, the mix ratio used was 1: 1.5:3. Ordinary Portland cement (OPC) of grade 42.5 N and Rice Husk Ash(RHA) were used at combination levels of 95/05, 90/10, 85/15, 80/20, 75/25 and 70/30 of OPC/RHA. These were used at water/binder ratios of 0.4, 0.45, 0.5, 0.55 and 0.6 respectively. The independent variables in this study are cement/water (c/w) and RHA/water (r/w) ratios by weight. The measured response obtained from the experiment is the compressive strength (f_{cu}) at 56 days of curing. Several researchers have monitored compressive strength of concrete at 56 days containing pozzolana [9, 11]. On this bases, the current research considered the strength of concrete at 56 days bearing in mind that the pozzolanic activity leads to low strength at lower ages with resultant high strength at greater ages.

2.1.1 Rice Husk Ash (RHA)

Rice husk, a by- product in the rice milling operation, is available as environmental waste in Minna, Niger State. The rice husk was burnt into ash in batches using a perforated platform having several holes of a size too small for rice husk to penetrate. This was placed on an enclosed floor slab. The slab separates the entire incinerator horizontally into two. The lower chamber is the source of heat heat and hot charcoal can be fed through the opening as indicated in Figure 1. The upper chamber has a compartment for inserting the rice husk for incineration. On top of the upper chamber, is a hollow platform in form of chimney where black smoke can escape during incineration. A cone of rice husk is formed around the chimney to completely cover the hollow platform. The rice husk at the small holes was ignited to incinerate it into rice husk ash (RHA) at 600°C. The temperature was measured using a thermopile. The ash obtained was allowed to cool for a period of time before being grinded into fine particles.

2.1.2 Cement

Ordinary Portland Cement (OPC) of grade 42.5 N available in Nigerian market was used.

2.1.3 Fine Ag Ngregates (Sand)

River sand obtained from Rafin Yashi at Bosso, Minnawas used. The sand was properly sieved and air dried to create no room for any organic/deleterious materials as well as removing the excess water on the surface of the soil particles.

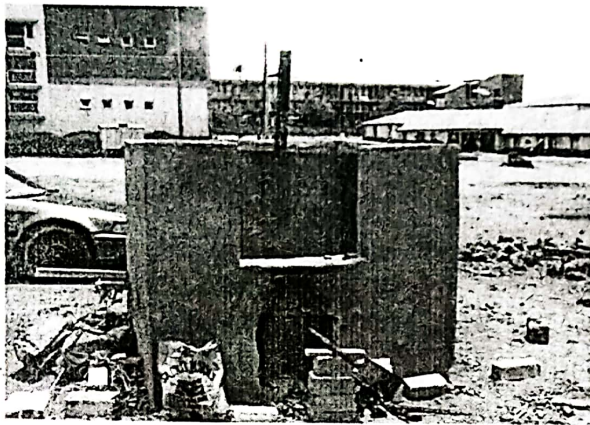


Figure 1: Brick wall Incineration chamber

2.1.4 Coarse Aggregates

Crushed granite rock popularly called chipping, purchased from commercial producers in Minna, Niger State was used. The maximum size of the aggregate was 20mm.

2.1.5 Water

The water used was potable drinking water from the Civil Engineering Laboratory, Federal University of Technology (FUT) Minna. The water is suitable for construction work [12].

2.2 Methods

Various tests were carried out on each major constituent material of the concrete as well as the fresh and hardened concrete in accordance with relevant British Standards. Materials tested are RHA, fine aggregates (sand) and coarse aggregates. The properties of the materials tested include oxide composition of the RHA in accordance with BS 4550: Part 2 1978 [13], sieve analysis, moisture content, specific gravity and aggregate impact value.

2.2.1 Mix Design

The mix design used for this work was based on Absolute Volume Method. The air content used was two percent (2%) [13]. The maximum size of the coarse aggregate used was 20mm. Each item or material constituting the concrete was finally obtained by weight (kg). Specific gravity of materials used were as obtained from the test experiments carried out on such materials before use and are listed in Table 1.

Table 1: Specific gravities of constituent materials of concrete

Constituent of concrete	Specific gravity
Ordinary Portland Cement (G_c)	3.15
Rice husk ash (G_r)	2.13
Fine aggregate (G_f)	2.66
Coarse aggregate (G_s)	2.86
Water (G_w)	1.00

If W is the weight, V is the volume and b, c, r, f, s & w represent binder, cement, RHA, fine aggregate, coarse aggregate and water respectively.

Then, weight of binder = W_b , Weight of cement = W_c , Weight of RHA = W_r , Weight of fine aggregate = W_f , Weight of coarse aggregate = W_s and Weight of water = W_w . Required mix ratio = 1: 1.5: 3. Then,

$$\frac{W_b}{W_f} = \frac{1}{1.5}; \quad W_f = 1.5W_b \quad (5)$$

Also,

$$\frac{W_b}{W_s} = \frac{1}{3} \text{ or } W_s = 3W_b \quad (6)$$

If water/binder ratio (w/b) = z , then,

$$W_w = zW_b \quad (7)$$

But binder(b) = cement(c) + RHA(r)

$$b = c + r$$

From 1; 1.5;3 $b = 1$, Then $c + r = 1$. That is $c = 1 - r$ and $r = 1 - c$. Here, r and c are fractions of 1

$$\begin{aligned} \text{From } b = c + r \text{ then } b &= cW_b + rW_b \\ &= (1-r)W_b + (1-c)W_b \end{aligned}$$

Thus

$$W_c = cW_b \quad (8)$$

and:

$$W_r = rW_b \quad (9)$$

From Absolute Volume Method

$$V_b + V_f + V_s + V_w + V_a = 1m^3 \quad (10)$$

Since allowable $V_a = 0.02m^3$

$$V_b + V_f + V_s + V_w = 1 - 0.02 = 0.98 \quad (11)$$

$$\text{But } V_b = V_c + V_r$$

$$\therefore V_c + V_r + V_f + V_s + V_w = 0.98 \quad (12)$$

$$\text{From } \text{Density} = \frac{\text{Mass}}{\text{Volume}} = \frac{\text{Weight}}{\text{Volume}}$$

Where density = ρ and weight = w ,

$$\rho = \rho w * G$$

Thus,

$$V = \frac{W}{\rho_w * G} = \frac{W}{1000 * G} \quad (13)$$

Substituting for the volumes in (12) gives

$$\frac{1}{1000} \left(\frac{W_c}{G_c} + \frac{W_r}{G_r} + \frac{W_f}{G_f} + \frac{W_s}{G_s} + \frac{W_w}{G_w} \right) = 0.98 \quad (14)$$

Substituting (5), (6), (7), (8), & (9) into 14 gives:

$$\begin{aligned} \frac{1}{1000} \left(\frac{cW_b}{G_c} + \frac{rW_b}{G_r} + \frac{1.5W_b}{G_f} + \frac{3W_b}{G_s} + \frac{zW_b}{G_w} \right) \\ = 0.98 \end{aligned} \quad (15)$$

$$\therefore W_b = \frac{980}{\frac{c}{G_c} + \frac{r}{G_r} + \frac{1.5}{G_f} + \frac{3}{G_s} + \frac{z}{G_w}} \quad (16)$$

$$\text{If } \frac{c}{G_c} = K_1, \frac{r}{G_r} = K_2, \frac{1.5}{G_f} = K_3, \frac{3}{G_s} = K_4, \frac{z}{G_w} = K_5$$

Then:

$$W_b = \frac{980}{K_1 + K_2 + K_3 + K_4 + K_5} \quad (17)$$

Equation (17) was used to arrive at the value for W_b which was also used to compute the remaining quantities.

2.2.2 Production of Concrete

For the purpose of this work, one hundred and fifty numbers of OPC+RHA concrete cubes were produced. Materials quantities for each set were measured separately as obtained from the mix design with the aid of an electronic weighing balance. The cement and rice husk ash (RHA) were mixed thoroughly before fine and coarse aggregates were introduced and also mixed together to obtain a homogenous mixture. The measured quantity of water was then added followed by thorough mixing to obtain a workable concrete. Slump test was conducted on the fresh concrete before placement in 150mm x 150 mm x 150mm metal moulds. The concrete in the moulds was tamped severally to acquire maximum compaction for expulsion of air voids. The concrete cubes were removed from the mould after 24hours and subsequently cured in a curing tank at 25°C with potable water.

2.2.3 Slump test

This test was carried out on all the mixes used for this work. It was used to determine the workability of the w/b ratios adopted for each mix. The slump test was conducted in accordance with BS 1881: Part 102 [15].

2.2.4 Compressive Strength Test

The compressive strength of the cube samples was obtained in accordance with the standard procedure given in BS 1881: Part 116 [16]. The samples were allowed to drain off before their weight were taken and recorded. This was followed by the crushing of the cubes. Five samples were crushed each for w/b ratio of 0.4, 0.45, 0.5, 0.55 and 0.60 at each replacement levels of 5%, 10%, 15%, 20%, 25% and 30% at 56th day of curing using the compressive testing machine in the Concrete Laboratory of Civil Engineering Department, Federal University of Technology, Minna. The test was conducted at loading rate within the range of 0.2 N/mm²/s to 0.4 N/mm²/s.

3. RESULTS AND DISCUSSION

3.1 Physical Properties of the constituent materials

Table 2 shows the physical properties of the constituent materials. The specific gravity of sand was found to be 2.66 which is marginally higher than 2.64 obtained by Oyetola and Abdullahi [17] but still within the range for natural aggregates of 2.6 and 2.7 as reported by Neville [9]. The mean specific gravity of RHA was found to be 2.13, a value very close to that obtained by [17, 18, 19]. The value thus obtained is within 1.9 and 2.4, a range for pulverized fuel ash (PFA) as reported by Neville [9]. However, the value obtained in this work is less than the value of 3.15 for Ordinary Portland Cement (OPC). This shows that RHA is lighter than cement.

Table 1: Physical Properties of the Constituent Materials

Properties	Experimental value
Fineness modulus of sand	2.98
Fineness modulus of RHA	0.73

Properties	Experimental value
Moisture content of sand	1.75
Moisture content of coarse aggregate	1.25
Specific gravity of sand	2.66
Specific gravity of coarse aggregate	2.86
Specific gravity of RHA	2.13
Aggregate impact value of coarse aggregate	10.75%

3.2 Chemical Analysis of Rice Husk Ash (RHA)

Table 3 shows the chemical composition of rice husk ash (RHA). The total percentage composition of silicon dioxide (SiO₂), aluminium oxide (Al₂O₃) and iron oxide (Fe₂O₃) was found to be 70.11%, a little higher than recommended minimum value of 70% for pozzolans by [20]. The value is lower than 73.15% obtained by [17], 73.56% obtained by [21], and 89.45% by [19] but slightly higher than 69.96% obtained by [22]. However the loss on ignition (LOI) of 13.33 is lower than 17.78% obtained by [17], 17.78% of [21] and 18.25% of [22]. This means that the RHA contains little unburnt carbon which tends to reduce the pozzolanic activity of the ash. However the ash is more effective than that obtained by [17, 21, 22]. It is good to mention that the LOI is higher than 5.81% by [19] and fairly close to 12% maximum recommended by [20]. This variation might be due to method of preparation and species of the rice husk. The chemical composition show that the RHA can be classified as Class F Pozzolana. This confirms that the rice husk ash (RHA) used in this work is a good pozzolan.

Table 3: Chemical Composition of Rice Husk Ash (RHA)

Oxide compounds	Oxide composition (%)
SiO ₂	68.28
Al ₂ O ₃	1.28
Fe ₂ O ₃	0.54
TiO ₂	0.07
CaO	0.37
MgO	3.59
MnO	0.13
K ₂ O	3.14
Na ₂ O	3.78
P ₂ O ₅	0.16
SO ₃	0.61
LOI	13.33

3.3 Slump of Concrete

Result of slump test in Table 4 shows that increase in replacement level of cement with RHA leads to decrease in the slump value for all levels of w/b ratio. This resulted in decrease in the workability even up to dry mixed concrete because of the absorptive cellular nature character of RHA particles. Reduction in workability causes compaction to be difficult thus leading to creation of air voids in the cubes, the cumulative resultant effect of which is reduction in the strength of the concrete.

Table 4: Slump for Concrete with w/b Ratios at Different RHA Levels (mm)

w/b ratio	5%RHA	10%RHA	15%RHA	20%RHA	25%RHA	30%RHA
0.4	25	10	10	5	-	-
0.45	30	20	10	5	-	-
0.50	35	20	10	5	-	-
0.55	85	50	15	10	-	-
0.60	140	120	35	25	20	10

3.4 Densities of Hardened Concrete

The density of RHA concrete was investigated as the ratio of the weighted mass of the concrete cube to the volume of the concrete cube [23]. From Table 5, for each w/b ratio the density decreases with increases in percentage RHA. However all the densities fall within the range of 2062.81kg/m³ and 2572.44kg/m³irrespective of the compressive strength value which indicates that concrete produced with cement replaced with up to 30% rice husk can be classified as heavyweight concrete. The result was also in tandem with values obtained by [24].

Table 5: Average Densities (kg/m³) of the Hardened Concrete Cubes

w/b	Replacement level with rice husk ash					
	5%	10%	15%	20%	25%	30%
0.40	2439.74	2296.30	2296.90	2187.90	2149.90	2103.72
0.45	2572.44	2357.93	2335.41	2327.11	2262.52	2144.00
0.50	2461.63	2454.92	2376.89	2265.48	2170.07	2131.55
0.55	2572.44	2556.44	2526.83	2272.59	2062.81	2199.11
0.60	2495.41	2495.41	2429.63	2435.56	2268.44	2160.59

3.5 Compressive Strength of Concrete

Table 6 shows the experimental data for the compressive strength of concrete. The experimental data obtained in this work was used to develop empirical model for compressive strength of RHA concrete at 95% Confidence Interval to find the line of best fit. The developed model is presented as equation 18. The output of the regression analysis gave standard deviation of 4.545, coefficient of determination of 74.8% and Adjusted coefficient of determination of 73.0%. This implies that the developed model has the ability to explain the variability in the experimental data by 73.0%. Also, the P values for the independent variables c/w, r/w as well as the constant E are 0.024, 1.47x10⁻⁹, and 1.95x10⁻⁸ respectively. These three P values are all less than 0.05 as shown in Table 7, an indication that there is significant relationship between the independent variables and the response which is the compressive strength (f_{cu}).

$$f_{cu} = -7.026 \frac{c}{w} - 42.467 \frac{r}{w} + 45.305 \quad (18)$$

Where A = -7.026 and B = -42.467 and E = 45.305

Whereas Hildegard and Hansen [11] obtained 32.62, 7.67 and -16.63 for A, B and E respectively for fly ash producing the model equation indicated as Equation 19.

$$f_{cu} = 32.62 \frac{c}{w} + 7.67 \frac{r}{w} - 16.63 \quad (19)$$

The predicted response for new compressive strength of fly ash (FA) concrete by [11] are in the range of 2.17N/mm² and 32.11N/mm² as against 1.16N/mm² and 30.81N/mm² obtained for RHA from Equation 18. The closeness in the range of values produced by these two models indicated that the model equation for RHA is suitable for use in estimating the compressive strength of Rice Husk Ash (RHA) concrete.

Table 6: Compressive Strength of Concrete at Various c/w and r/w

c/w	r/w	Compressive strength (f _{cu}) N/mm ²
2.37	0.13	27.37
2.11	0.11	24.73
1.9	0.1	26.39
1.73	0.09	30.00
1.58	0.08	24.15
2.25	0.25	13.24
2.0	0.22	23.25
1.8	0.2	34.04
1.64	0.18	27.73
1.5	0.17	23.64
2.13	0.38	6.75
1.89	0.33	16.84
1.7	0.30	28.45
1.55	0.24	30.98
1.42	0.25	20.49
2.00	0.50	5.50
1.78	0.44	12.41
1.6	0.4	22.14
1.45	0.36	21.74
1.33	0.33	22.39
1.87	0.63	5.59
1.67	0.56	8.93
1.5	0.50	18.97
1.36	0.46	12.32
1.25	0.42	17.32
1.75	0.75	3.77
1.56	0.67	6.82
1.40	0.6	13.72
1.27	0.55	8.04
1.17	0.5	12.00

Table 7: Coefficients of the Equation and their P Values

Independent variables	Coefficient	P values	Significant level
Constant	45.206	1.95x10 ⁻⁸	Very significant
c/w	-7.026	0.024	Very significant
r/w	-42.5	1.47x10 ⁻⁹	Very significant

3.6 Diagnostic Plots of the Residuals

Several graphical plots were obtained to show the capability of the fitted linear model. Figures 2 and 3 show the scattered plots of the compressive strength against r/w ratio and c/w

ratios respectively. The experimental points are scattered about the mean residual value of zero (0). This is an indication of a good model.

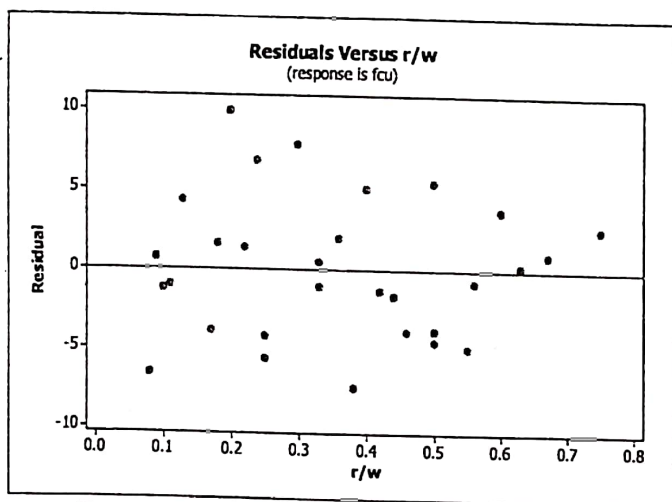


Figure 2: Scatter Diagram of f_{cu} Residual Versus r/w

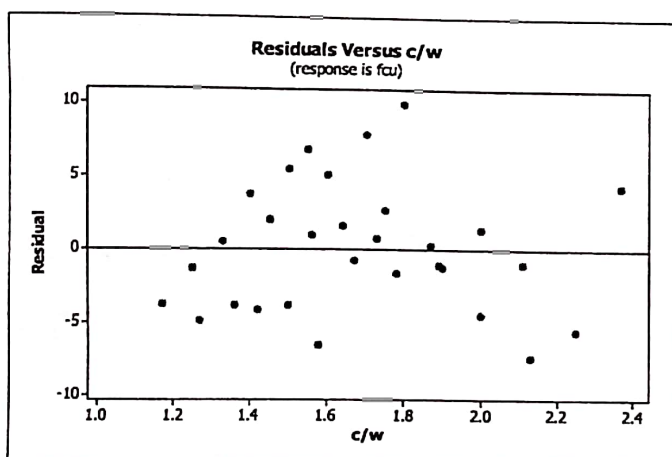


Figure 3: Scatter Diagram of f_{cu} Residual Versus c/w

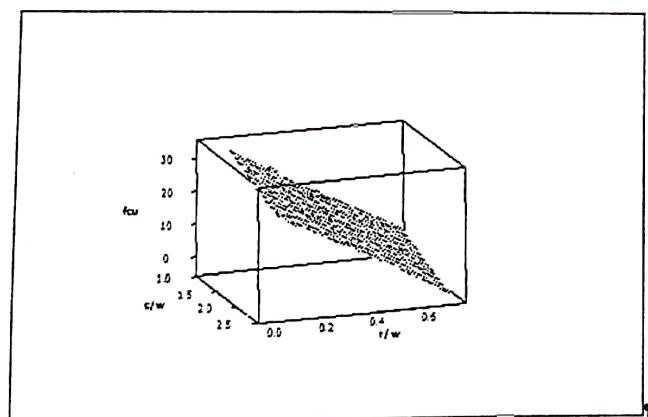


Figure 4: Surface Plot of f_{cu} vs $r/w, c/w$

3.7 Surface Plot of the Linear Polynomial Model.

Figure 4 shows the surface plot of the developed linear model. It gives the pictorial view of the behaviour of the underlying relationship. The plot shows a steeper slope for r/w ratio compared to c/w ratio. This is also evident from Equation 18. This implies that r/w ratio have significantly negative influence the compressive strength of concrete compared to c/w ratio. Equation 18 has positive constant term and the variables c/w

and r/w ratios have negative slopes. This implies that increase in the value of any of the variable will lead to a decrease in the corresponding values of the compressive strength.

4. CONCLUSION

From the outcome of this work, the following conclusions can be deduced:

- The rice husk ash obtained belongs to Class F Pozzolana and is pozzolanic since the sum of the percentage of silica, alumina and ferric oxide above 70%.
- The range of the best water/binder ratio was found to lie between 0.50 and 0.55 as the concrete was very workable at this w/b ratio for the replacement of cement with RHA after 15%.
- The experimental data was fitted into the hypothetical model with the line of best fit obtained from the model given as $f_{cu} = -7.026 \frac{c}{w} - 42.467 \frac{r}{w} + 45.305$
- The compressive strength of hardened RHA concrete depends on cement-water (c/w) content and rice husk RHA - water (r/w) content.

5. REFERENCES

- Rao, P. P., Kumar, A. P. and Singh B. B. "A Study on Use of Rice Husk Ash in Concrete", *International Journal of Education and Applied Sciences*, Vol. 4, Number 2,, pp 75-81. 2014.
- Macginley, T. J. and Choo, B. S. *Reinforced Concrete; Design Theory and Examples*, E. and F. N. Spon, Chapman and Hall London, 1990.
- Mosley, J. H. and Bungey, J. H. *Reinforced Concrete Design*, Macmillan Press, London, 1991.
- Edeh, J. E., Samson, I. and Terhembra, A. "Rice-Husk Ash-Carbide-Waste Stabilisation of Reclaimed Asphalt Pavement", *Nigerian Journal of Technology*, Vol. 35, Number 3, pp 465-472. 2016, [5] Okonkwo, U. N. and Agunwamba, J. C. "Classical Optimisation of Bagasse Ash Content-Stabilised Lateritic Soil". *Nigerian Journal of Technology*, Vol. 35, Number 3, pp 481-490. 2016.
- Ndububa, E. E., Okonkwo, J. S. And Ndububa, O. I. "The Potential Use of Fonio Husk Ash as Pozzolana in Concrete". *Nigerian Journal of Technology*, Vol. 35, Number 1, pp 31-36. 2016.
- Akeke, G. A., Ephraim, M. E. and Ukpata, J. O. "Compressive Strength of Concrete With Rice Husk as Partial Replacement of Ordinary Portland Cement", *Scholarly Journal of Engineering Research*, Vol. 1, Number 2, pp 32-36 2012.
- Reddy, B. D., Jyothy, A. and Reddy, I. V. R. "Effect of Rice Husk Ash on The Properties of Ordinary Portland Cement and Portland Slag Cement with and Without Super plasticizers", *International Journal of Civil, Structural, Environmental and Infrastructure Engineering Research and Development*, Vol. 3, Number 2, pp 1-8. 2013.

- [9] Neville, A. M. *Properties of Concrete*, Longman Scientific and Technical Publishing, London, 1995.
- [10] Popovic, S. *Strength and Related Properties of Concrete: A Quantitative Approach*, John Wiley and Sons, London, 1998.
- [11] Hedegaard, S. E. and Hansen, T. C., "Modified Water Cement Ratio Law for Compressive Strength of Fly Ash Concrete", *Materials and Structures*, Vol. 25, pp 278-283. 1992.
- [12] BS 3148 "Methods of Test for Water for Making Concrete", British Standard Institution, Her Majesty Stationary office London, 1980
- [13] BS 4550: Part 2. "Chemical Test", British Standard Institution, Her Majesty Stationary office London, 1978.
- [14] ACI Committee 211.1-91. "Standard Practice for Selecting Proportions for Normal, Heavyweight and Mass Concrete", Detroit, American Concrete Institute.
- [15] BS 1881: Part 102. "Method for Determination of Slump of Fresh Concrete", British Standard Institution, Her Majesty Stationary office London, 1983.
- [16] BS 1881: Part 116. "Method for Determining Compressive Strength of Concrete Cubes", British Standard Institution, Her Majesty Stationary office London, 1983.
- [17] Oyetola, E. B and Abdullahi, M. "The Use of Rice Husk Ash in Low-Cost Sandcrete Block Production", *Leonardo Electronics Journal of Practices and Technology*, Vol. 8, pp 58-70. 2004.
- [18] Joaquim, S., Coutinho, J. S. and Sampaio, M. N. Portuguese Rice Husk Ash as Portland cements Replacement. U.S. Patent no 5329867, 1994.
- [19] Habeeb, A. G. and Mahmud, B. H. "Study on Properties of Rice Husk Ash and Its Use as Cement Replacement Material", *Journal of Material Research*, Vol. 13, Number 2, pp 185-190. 2010.
- [20] ASTM- American Society for Testing and Materials C 618 "Standard Specification for Coal, Fly Ash and Raw or Calcined Natural Pozzolan for Use in Concrete". 4 (04), 1994.
- [21] Ogunbode, E., Hassan, I. O., and Isa, R. B. "An Evaluation of Compressive Strength of Concrete made with Rice Husk Ash obtained by Open Air Burning", *Environmental Technology and Science Journal*, Vol. 4, Number 1, 2011, pp 137-147.
- [22] Dabai, M. U., Muhammad, C., Bagudo, B. U. and Musa, A. "Studies on the Effect of Rice Husk Ash as Cement Admixtures", *Nigerian Journal of Basic and Applied Science*. Vol. 17, Number 2, pp 252-256. 2009.
- [23] Akeke, G. A, Ephraim, M. E, Akobo, I. Z. S, and Ukpata, J. O. "Structural Properties of Rice Husk Ash Concrete", *International Journal of Engineering and Applied Sciences*. Vol. 3, Number 3, pp 57-62. 2013,
- [24] Reynolds, E. C. and Steedman, C. J. *Reinforced Concrete Designers Handbook*. Spon Press, Taylor and Francis Group London, 1988.