



INVESTIGATION INTO THE GEOTECHNICAL PROPERTIES OF SELECTED LATERITIC SOILS FROM MINNA AS PAVEMENT MATERIALS

Ob'lama, E.J.^{1,2}, Amadi, A.A.², Alhaji A.A.², Alhassan, M.², Adejumo, T.W.E.²

¹Department of Civil Engineering, The Federal Polytechnic, Bida

²Department of Civil Engineering, Federal University of Technology, Minna

Abstract

This study presents an evaluation of some geotechnical properties of selected lateritic soil samples around Minna, Niger State for pavement application. Sixteen (16) lateritic soil samples were collected from five borrow pits within the study area. The samples were subjected to physical, mineralogical, index, compaction and strength properties tests. The samples were further characterized according to AASHTO and USC systems. The natural moisture content values of samples ranged between 2.03-34.24%. Specific gravity values were in the range of 2.47-2.70 while bulk density ranged between 1.76-2.09g/cm³. The particle size analysis showed that ten (10) of the lateritic soil samples were gap-graded while six (6) were poorly graded. Eleven (11) of the samples had more than 35% of their constituent passing sieve No.200 (0.075 mm), while five (5) of the samples have less than 35% fines content. The compaction relationship of samples compacted at British Standard Light energy gave values between 1.52-1.96g/cm³ and 9.2 - 20.6% for MDD and OMC respectively. Strength property evaluation of samples revealed an average unsoaked CBR value of 11.78% with a range of 0.1–5 kPa for unconfined compressive strength. Results from XRD showed that all samples except PG3 contain Kaolinite mineral in varying proportion. Quartz mineral were found in the range of 20.83-76.45%. Clay minerals were generally less than 7%. Based on plasticity index and liquid limit requirements, five (5) of the test samples are suitable for base course application, while only one (1) samples met the requirements as sub-grade material. Ten (10) of the samples will require some forms of treatment to improve or remedy their engineering deficiencies in pavement or other applications.

Keywords: *Index Property, Lateritic soils, Marginal materials, Pavements, Strength*

1. INTRODUCTION

The need for cost effective and efficient transportation facilities in any economy cannot be over emphasized. Functional transportation facilities play a vital role in fast tracking socio-economic growth, poverty alleviation and development in general. For developing economies like Nigeria, roads are the most accessible forms of transportation. Sharma (2012) compared roads to the arteries of the human body which are vital for survival. This is because they act as essential catalysts for initiating and sustaining meaningful goals and agenda aimed at development. For a country like Nigeria an approximate land area of 924,763 km², huge networks of roads are required to effectively serve the people.

Considering the high cost of building new roads and the frequent structural failures associated with existing roads, development of cost effective standard durable all-weather roads is a major challenge to engineers. Amu *et al.* (2011) noted that though many reasons account for structural failures of many Nigerian roads, the principal cause is attributed to the use of sub-standard material. Eze-Uzoamaka (1981) observed that

most aggregates used in pavement construction lack the requisite engineering quality for use. Materials which lack adequate strength cannot withstand traffic stresses especially under varying moisture conditions. The use of such materials gradually leads to their deterioration under working load. These subsequently lead to pavement failures which require frequent maintenance.

The design and construction of durable pavement components with the capacity to withstand loads is a serious challenge to stakeholders in the road industry. This is due to the high cost of road construction using high quality conventional materials. The use of conventional materials are no longer a viable option but the adaptation local materials using relevant techniques which satisfy both traffic and maintenance needs at minimal cost.

Laterites are highly weathered and altered residual soils formed by in-situ weathering and decomposition of rocks under tropical conditions (Elarabi, Taha and Elkhawad; 2013). Lateritic soils are surface soil formations enriched with iron, Aluminum, manganese with some titanium developed by intense and long



lasting weathering of parent rock (McFarlane, 1976). They are usually reddish, brown or yellowish in colour. In Nigeria, these soil groups are adjoined primary construction materials especially in road construction (Faluyi and Amu, 1989; Uche, 2007; Mttalib, 2008; Mu'azu, 2009; Omotosho and Eze-Uzoamaka, 2008; Amadi, 2010; Ogunribo, 2011; Amu *et al.*, 2011; Osinubi, 1998).

In this vein, diverse researches aimed at exploiting and adopting local available materials like Lateritic soils for construction are ongoing (Osinubi *et al.*, 2017; Ayeni, 2016; Manasseh & Joseph, 2015; Dada and Faluyi, 2015; Bello *et al.*, 2015; Mustapha *et al.*, 2014; Ogunribido, 2011; Bwalya, 2009). According to Amadi (2010) consideration of lateritic soils for use as construction materials should be based on a thorough evaluation and understanding of their inherent characteristics necessary to predict their engineering performance. Results from such researches possessing the requisite engineering quality will be adopted aimed at providing cheaper, stable and more durable pavements.

Pavements are made up of superimposed components of carefully selected and processed materials. These components are expected to bear and distribute imposed loads in a manner that the natural ground formations are not unduly stressed. For this reason, materials which make up these components are therefore expected to possess minimal engineering specifications. According to Singh (2002), pavements are relatively stable crust of material over the natural soil formation for the purpose of supporting and distributing wheel loads while providing an adequate wearing surface. The designs of pavement are aimed at attaining a structure that is stable, durable and free from any forms of defects. Osinubi (1998) observed that low cost roads are not of poor quality but cost effective and capable of being maintained at low recurring cost.

Lateritic soils are often referred to as *marginal* or *non-standard* materials due to their peculiar behaviour in construction. Marginal materials are usually not wholly in conformity with the specification in use in a country or region for normal road materials. Faluyi and Amu (1989) noted however that most Nigerian lateritic soils contain Kaolinite as predominant clay mineral. They are therefore not out rightly *problematic* soils as portrayed in certain literatures. The most viable option in their use is to alter such materials with the aim of improving specific engineering properties relevant for their use. Such materials can be used successfully with project adaptation (Cook and Gourley, 2002).

Road Note 31 (1977) encourages the use of available local materials with emphasis on reliable results from performance evaluation studies while incorporating any special feature for their satisfactory usage. The key to

successful innovative solution is to challenge conventional assumptions with regards to design and construction where locally available materials are used (Cook and Gourley, 2002).

2. MATERIALS AND METHODS

The lateritic soil samples used in this study were obtained from five (5) selected borrow pits around Minna; Niger State. Minna is located in North-central Nigeria between latitude 9° 36' 50" North and longitude 6° 33' 25" East. Geologically, the study area lies within the Northern central basement complex of Nigeria. The area is characterized by migmatite gneiss complex, older granite and schist (Ajibade, Rahaman and Egezi; 1988). The maximum rainfall per year is between 1000 to 1500mm drained by several rivers which are tributaries of the river Niger (Alhassan and Mustapha, 2012).

A total of sixteen (16) lateritic soil samples were collected by method of disturbed sampling during the dry season. Samples were collected from five (5) different axis around Minna, the capital of Niger State. Samples were collected between 0.5-1.0m below the natural ground level. Samples were put in air tight bags, marked and sealed to preserve their natural moisture. Sample labels indicated date of sampling; locations and depth of sample collection. Samples were immediately transported to the Geotechnical Laboratory of the Civil Engineering Department of the Federal University of Technology; Minna (Gidan Kwano campus). Natural moisture content tests were performed on soil samples immediately on arrival at the laboratory. Other tests were conducted in the Soil Mechanics Laboratory of the Federal Polytechnic, Bida, Niger State, Nigeria.

Samples MK1, MK2 and MK3 were collected from active borrow pits at Maikunkele at the northern axis of Minna. Samples labeled JT1, JT2, JT3 were collected from a relatively active borrow pits at Jatai, a village along Minna-Sarkin Pawa road on the eastern axis of Minna. On the Minna-Suleja road axis, three samples labeled PG1, PG2 and PG3 were collected from active borrow pits located at Poggo. Samples LG1, LG2 and LG3 were collected from active borrow pits at Lapia Gwari near Talba farm estate. Four samples; GK1, GK2, GK3 and GK4 were collected from the Gidan Kwano campus of the Federal University of Technology; Minna along Bida-Minna road axis.

2.1 Laboratory evaluation of lateritic soil samples

Laboratory tests were performed in accordance to BS 1377(1990): Methods of test for soil for civil engineering purposes. Physical and geotechnical investigations conducted on collected lateritic soil samples included:

1. Natural moisture content determination of test soil samples.
2. Bulk density determination of soil test samples.
3. Particle density (specific gravity) determination of soil test samples.

4. Particle size distribution of soil test samples (Dry and Wet sieve analysis)
5. Determination of Atterberg limits values of soil samples.
 - i. Determination of Liquid Limit, (LL) (Cone penetration method).
 - ii. Determination of Plastic Limit, (PL).
 - iii. Determination of Plasticity Index, (PI).
 - iv. Determination of linear shrinkage values of soil test samples.
5. Determination of density/moisture relationship by the British Standard Light (BSL) method.
6. Determination of California Bearing Ratio (CBR) values for soil samples.
7. Determination of the Unconfined Compressive Strength (UCS) values of soil samples.

LG3	9.16	2.63	1.98	Red
GK1	3.12	2.63	1.96	Reddish Brown
GK2	10.95	2.60	1.83	Reddish Yellow
GK3	6.69	2.58	1.91	Light Reddish Brown
GK4	2.03	2.55	2.02	Yellowish Brown

3. RESULTS AND DISCUSSION

Results of physical, index, strength and mineralogical investigations produced results discussed as follows. Natural moisture content average value was 11.15% from a range of 2.03 – 34.24 % was obtained. Specific gravity values were within 2.47 – 2.70 with mean value of 2.61. Bulk density values were between 1.76 – 2.09 g/cm³ with an average value of 1.89g/cm³. Details of these test results are summarized in Table I.

3.1 Consistency Properties of Lateritic Soil Samples

Consistency limits describe the behaviour of fine grained soils in the presence of moisture. The presence of clay minerals in soils allows them to be remolded in the presence of moisture without crumbling. Consistency or Atterberg limits are defined by Liquid limits, LL; plastic limits, PL and shrinkage limit. Liquid limits, LL and Plastic Limits PL provide a significant way of identifying fine grained cohesive soils. The difference between the LL and PL known as plasticity index, PI.

TABLE 1: PHYSICAL PROPERTIES OF LATERITIC SOIL SAMPLES

Test	Natural moisture content, w (%)	Specific Gravity, (G _s)	Bulk density, ρ _b (g/cm ³)	Colour
MK1	4.75	2.56	2.09	Dark Reddish Grey
MK2	22.34	2.62	2.76	Reddish Grey
MK3	34.24	2.47	2.75	Grey
JT1	2.20	2.50	2.03	Light Grey
JT2	2.08	2.59	1.98	Reddish Yellow
JT3	3.24	2.65	1.96	Reddish Brown
PG1	13.9	2.61	1.79	Dusty Red
PG2	12.43	2.62	1.87	Light Red
PG3	11.99	2.63	1.80	Light Reddish Brown
LG1	21.35	2.70	1.86	Light Grey
LG2	20.0	2.65	1.82	Red

Osinubi, Eberumu, Bello and Adzegah (2012) observed that soils with too high LL were susceptible to desiccation cracking. Soils with high PL were less workable linear shrinkage values are useful for establishing likely conditions of expansion on wetting of soils hence are useful for quantifying the amount of shrinkage likely to be experienced by clay soil materials. Liquid Limits (LL) values from consistency tests were variable. LL values were between 17.7 and 62.2% with mean value of 35.59%. Plastic limits (PL) values of the lateritic soil samples ranged from non-plastic (NP) to 31.6%, and an average value of 17.28%. Plasticity Index values were between 1.2 and 30.6% with average value of 18.3%. The federal ministry of works and housing FMWH(1997) specified a maximum LL value of 35% and 30% respectively for sub-grade and sub-base materials. Corresponding PI values of 12% and 10% is given for sub-grades and sub-bases. For base courses, maximum values of 30 and 10% are specified for LL and PI respectively. Investigations for linear shrinkage reveal an average value of 8.18% within a range of 1.0 – 12.0%. Consistency values are presented in Table II.

TABLE II: CONSISTENCY VALUES OF LATERITIC SOIL SAMPLES

Sample No	Liquid Limit, LL (%)	Plastic Limit, PL (%)	Plasticity Index, PI (%)	Linear Shrinkage (LS)	Remarks on Plasticity
MK1	43.6	25.9	17.7	11.5	Med Plasticity
MK2	51.7	30.1	21.6	10.0	High Plasticity
MK3	62.2	31.6	30.6	14.5	High Plasticity
JT1	18.0	16.8	1.2	3.5	Low Plasticity
JT2	25.2	15.7	9.5	6.5	Med Plasticity
JT3	17.8	NP	17.8	3.0	High Plasticity
PG1	30.0	16.5	13.5	11.0	Med Plasticity
PG2	34.8	21.9	12.9	9.0	Med Plasticity
PG3	39.1	24.6	14.5	11.0	Med Plasticity
LG1	35.1	NP	35.1	1.0	High Plasticity
LG2	41.4	11.4	30.0	10.0	High Plasticity
LG3	54.0	24.7	29.3	12.0	High Plasticity
GK1	17.7	NP	17.7	3.0	High Plasticity
GK2	44.6	26.5	18.1	9.0	High Plasticity
GK3	26.3	16.2	10.1	7.0	Med Plasticity
GK4	28.0	14.5	13.5	9.0	Med Plasticity

NP = Non-Plastic

3.2 Gradation Characteristics of Lateritic Soil Samples

The aim of any gradation analysis is to determine the particle sizes distribution of soil samples. The resultant grading curves are graphical representation of the particle size distribution. They are useful means of describing a soil. They are the basis for soil classification and a means of predicting their behaviour. Figure 1 shows the obtained grading curves from the particle size analysis test. Twelve of the soil samples had more than 35% of their constituents passing the BS 200 sieve. The gradation curves show that samples were either poorly graded or gap graded as noted by Amu *et al* (2011). Samples MK₁, JT₃, LG₁ and GK₁ had less than 35% of their constituents passing the 75µm sieve. Samples MK₁, JT₃, LG₁ and GK₁ had fines content of 24.5%, 30.1%, 31.3% and 32.65% respectively. Sample MK₃ is gap graded with the most fines content of 90.1%.

TABLE III: FINES CONTENT OF LATERITIC SOIL SAMPLES

Sample Label	Percentage Passing BS sieve No 200(%)	Remarks on Grading Curve	Predominant constituent Materials
MK1	24.5	Gap graded	Sandy gravel
MK2	76.8	Gap graded	Sandy Gravel
MK3	90.1	Gap graded	Clayey soil
JT1	36.4	Poorly graded	Sandy gravel
JT2	41.5	Poorly graded	Sandy gravel
JT3	30.1	Poorly graded	Sandy gravel
PG1	54.5	Gap graded	Sandy soil
PG2	61.1	Gap graded	Sandy soil
PG3	70.1	Gap graded	Sandy soil
LG1	31.3	Gap graded	Sandy soil
LG2	66.7	Poorly graded	Sandy soil
LG3	63.3	Gap graded	Sandy soil
GK1	32.6	Gap graded	Gravel Sand
GK2	64.3	Poorly graded	Sandy gravel
GK3	56.0	Gap graded	Gravel Sand
GK4	40.4	Poorly graded	Gravel Sand

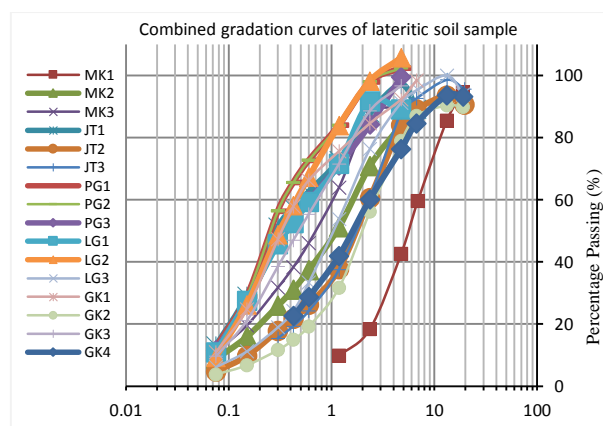


FIGURE 1: COMBINED GRADATION CURVES OF TEST SAMPLES

3.3 Compaction Characteristics of lateritic soil samples.

Compaction is an indication of the state of stability of a soil for construction. Compaction tests are used to establish the dry density/moisture content relationship of soils under controlled conditions used as a standard for comparison in field condition. The compaction characteristics of the individual lateritic soil samples were determined in the laboratory by the British Standard Light (BSL) method. The compaction characteristics also referred to as the moisture density relationship included maximum dry density (MDD) and optimum moisture content (OMC). The range of MDD values were between 1.52 – 1.96g/cm³ with mean value of 1.77g/cm³. The mean optimum moisture content was 14.68% from a range values of 9.2% – 20.6% as shown in Table III.

TABLE III: COMPACTION PROPERTIES AND STRENGTH VALUES OF LATERITIC SOIL SAMPLES

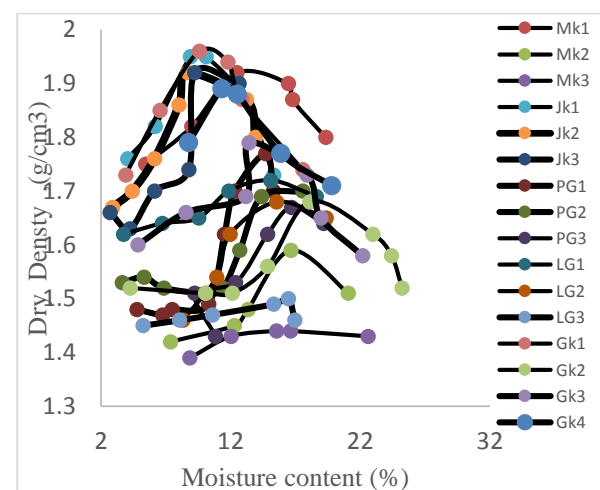


FIGURE 2: COMBINED PLOTS OF MOISTURE/DENSITY RELATIONSHIP OF LATERITIC SOIL SAMPLES

3.4 Strength characteristics of test samples

Strength is an important property of any soil. Two strength characteristics were evaluated. They include California Bearing Ratio (CBR) and Unconfined Compressive Strength (UCS).

The California bearing ratio (CBR) test is a semi-empirical test used in the estimation of the strength of or bearing capacities of pavement components. It measures the resistance which is equivalent to the difficulty to penetration under specified density and moisture conditions. The CBR rating is proportional to the resistance to penetration. The average unsoaked CBR value is 11.78% from a range value of 1.12-26.02%. These are below the FMWH Specification of 30% for non-dry soil purpose for use as sub- base material.

The maximum value of compressive force per unit area which a soil specimen can sustain is referred to as the unconfined compressive strength of the soil. The

method adopted in this study is that of the definitive load frame. Values of Unconfined Compressive Strength were in the range of 0.1 – 5 KPa.

Table IV: COMPACTION AND STRENGTH PROPERTIES RESULTS

Sample Identity	Compaction Characteristic Tests		Strength Property Tests	
	MDD(g/c m ³)	OMC (%)	CBR (%)	UCS (kPa)
MK1	1.92	14.6	12.84	4.71
MK2	1.61	20.6	1.12	3.92
MK3	1.52	17.0	1.12	0.10
JT1	1.93	9.2	20.70	1.37
JT2	1.93	10.0	15.08	3.82
JT3	1.96	9.6	26.02	5.00
PG1	1.75	14.7	10.99	3.92
PG2	1.70	17.0	12.90	3.82
PG3	1.68	17.6	6.55	2.35
LG1	1.72	15.0	12.40	1.08
LG2	1.69	16.0	19.84	3.14
LG3	1.62	20.3	12.71	3.14
GK1	1.96	9.6	20.83	2.16
GK2	1.68	18.0	15.22	3.33
GK3	1.79	14.0	2.81	2.45
GK4	1.89	11.6	11.12	2.45

TABLE V: THE LATERITIC SOIL SAMPLES ACCORDING TO THEIR CLASSES AND PAVEMENT RATING

Sample Label	Soil Classification	
	AASHTO	USCS
MK1	A-2-6	GC,SC
MK2	A-7-5	OH,MH
MK3	A-7-5	OH,MH
JT1	A-6	CL
JT2	A-4	MH
JT3	A-2-6	OH
PG1	A-6	GC,SC
PG2	A-6	CL
PG3	A-6	CL
LG1	A-3	SM
LG2	A-7-6	CH,CL
LG3	A-7-6	CH,CL
GK1	A-2-6	ML,OL
GK2	A-7-6	CH,CL
GK3	A-4	ML,OL
GK4	A-6	CL

3.5 Sample Identification and classification

The Lateritic soil samples were classified according to both AASHTO and Unified Soil Classification System (USCS). Three (3) of the soil samples; MK1, JT3 and GK1 can be classified as A-2-6 soils. These groups of soil according to USC can be classified as GC or SC soils. Only one test sample, LG1 fell into A-3 group of soils in accordance to AASHTO, corresponding to SP on USCS. Two (2) soil samples; JT2 and GK3 were grouped as A-4 soils class based on AASTO classification which corresponds to MH or OH on the USCS. Four soil samples; JT1, PG1, PG2 and GK4 were classified as CL and A-6 on the USCS and AASHTO classification schemes respectively. Based on AASHTO classification schemes, samples MK2 and MK3 can be classified as A-7-5 which corresponds to OH or MH in the USCS. Four samples, samples JT3, LG2, LG3 and GK2 are A-7-6 which according to USCS can either be GC or SC as shown in Table V. Classification and pavement rating of test lateritic samples are shown in Table VI.

3.6 Mineralogical Composition of Lateritic Soil Samples

Results from X-ray diffraction, (XRD) gave a wide range of mineralogical constituents in varying proportion. These minerals include; Kaolinite, Montmorillonite Albite, Albite (calcian low), Muscovite, Halloysite, Illite, Potassium Aluminium Silicate Hydrate, Sodium Magnesium Aluminium Oxide, Beidellite, Sepiolite, Silicon and quartz. Quartz being the predominant mineral with a range value of 20.0% -93.2% as indicated in Table VII. The quantity of Kaolinite for the samples were in the range of 4.17-7.78%. Sample LG2 contained 8.33% Montmorillonite clay mineral. Sample PG3 contained Illite and Halloysite clay minerals each in 2.08% proportion. Sample MK3, a highly plastic gap-graded clayey soil with a natural moisture content equivalent to 34.24% and a fines content of 90.1% contain 1.45% muscovite mineral.

TABLE VI: AASHTO CLASSIFICATION AND RATING OF TEST SAMPLES

Sample Label	Soil Class	Typical Soil description of soil class	General Rating as Sub-grade Materials
MK1,GK1,JT3	A-2-6	Silty Clay materials (More than 35% of total sample passing No,200 sieve	Excellent to good materials
LG1	A-3	Fine sands with silty or clay fines or small amount of non-plastic silt	Excellent to good materials
JT2,GK3	A-4	Non-plastic or moderately plastic silty soils	Fair to Poor materials
PG1,PG2,PG3	A-6	Plastic clays having 75% or more fines.	Fair to poor materials
JT1,GK4 MK2,MK3	A-7-5	Clay materials with moderate PI in relation to LL.	Fair to poor materials
LG2,LG3,GK2	A-7-6	Materials have high PI in relation to LL.	Fair to poor materials

TABLE VII: MINERALOGICAL COMPOSITION OF SELECED LATERITIC

Name of Mineral	Quantities (%)					
	MK3	JT2	PG3	LG1	LG2	GK3
Sample name						
Quartz	70.45	50.40	20.83	70.45	76.45	50.0
SiO ₂						
Kaolinite	6.38	4.20	-	6.38	6.38	4.17
Al ₂ (Si ₂ O ₅)(OH) ₄						
Kaolinite IMD	4.77	1.57	-	2.39	4.77	1.56
Al ₂ Si ₂ O ₅ (OH) ₄						
Silicon	2.08	--	-	--	-	-
Albebite	-	4.20	10.42	25.0	3.1	4.17
NaAlSi ₃ O ₈						
Halloysite	-	-	2.08	-	-	-
Illite	-	-	2.08	-	-	-
Potassium Aluminium Silicate Hydrate	-	-	8.33	6.08	-	-
K100A						
Sodium Magnesium Aluminium Oxide				3.12		
Montmorillonite					8.33	
Muscovite	-	-	-	-	-	1.45
Beidellite	-	-	-	1.21	-	-
Sepiolite	-	-	-	2.51	-	-

4 CONCLUSIONS

1. The lateritic soil samples studied included soils of A-2-6, A-3, A-4, A-6, A-2-5 and A-7-6 soil groups on the AASHTO classification system. These correspond to GC, MH, CL, SP, CH and SC according to Unified Soil Classification Scheme (USCS).
2. Based on plasticity index and liquid limit requirements, five (5) of the test samples are suitable for application as pavement components. Only sample JT3 met the requirements for use as base course material. Ten (10) of the samples will require some forms of treatment to improve or remedy their engineering deficiencies.
3. The average moisture content value for the lateritic soil samples is 11.5%. Values of specific gravity ranged 2.47-2.7 while that for bulk density is between 1.76-2.09g/cm³. Other Index property values were 17.7-62.25% for LL.. Plasticity ranged from low to high plasticity with linear shrinkage value of 8.18 % on the average.
4. The mean Optimum Moisture Content (OMC) value for compacted samples is 14.7% average Maximum Dry Density value of 1.77g/cm³. Strength properties evaluation showed that the lateritic soil samples had average unsoaked CBR values of 11.78% with unconfined compressive strength in the range 0.1–5 kPa.

5. Mineralogical content evaluations from X-ray diffraction (XRD) analysis for the test samples revealed clay minerals such as Montmorillonite, Halloysite, Muscovite and Illite. Only sample LG2 contained Montmorillonite mineral at a value of 8.33%. The quartz content for the soil samples were in the range of 20.83-76.45%.
6. Ten (10) samples, MK2, MK3, JT2, PG1, PG2, PG3, LG1, LG2, LG3 and GK3 did not meet the requirement for use as pavement materials. For effective utilization, they need to be treated to meet minimum specifications for use as pavement components.

REFERENCES

- Afeez, A.B., Joseph, A.I. and Hahmed, A. (2015). Stabilization of Lateritic Soils with Cassava Peel Ash. *British Journal of Applied Science and Technology*, 7(6): 642 – 650.
- Alhassan, M and Mustapha, A.M. (2007). Effects of Rice Husk Ash Cement Stabilized Laterite. *Leonardo Electronic Journal of Practices and Technologies*. Iss.11, 47-58.
- Amadi, A. A. (2010). Evaluation of Changes in index properties of lateritic soils stabilized with fly ash – *Leonardo Electronic Journal of Practice and Technology*. Issue 17, 69 – 78.
- Ayeni, O. (2016). Enhancing some geotechnical characteristics of laterite soils using limestone ash wastes.
- Bello, A.A., Ige, J. A. and Ayodele, H. (2015). Stabilization of Lateritic soil with cassava peel ash. *British Journal of Applied Science and Technology*. 7(6): 642 – 650.
- B.S.1377:1990: British Standard Method of Tests for civil engineering purposes. *British Standards Institute*. London, United Kingdom.
- Cook, J.R and Gourley, C.S (2002) “A frame work for the Appropriate use of Marginal Materials”. Being a paper presented at the World Road Association (PIARC) –, June, 2002.
- Dada, M.O. & Faluyi, S.O. (2015). Physical Properties of Lime – Bamboo leaf ash treated samples of lateritic soils in Ado – Ekiti, Nigeria. *Global Journal of Technical Committee C12 seminar in Mongolia Engineering Designs and Technology*. ISSN: 2319 – 7293, 4(4) 4 – 8.
- Eze – Uzomaka O.J (1981) “Appropriate technology solution to problems of Nigeria Road Industry”. *Appropriate Technology in Civil Engineering*. ICE London, 21– 23.
- Faluyi, S.O and Amu, O.O (1989) Effects of lime stabilization on the pH values of lateritic soil in Ado-Ekiti – Nigeria. *Journal of Applied Sciences*, 5(1): 190 – 192
- Mttalib M.O. A.(2008). Atterberg limits properties of laterite soil admixed with lime-Rice husk Ash. *Journal of Engineering and Technology (JET)*; Faculty of Technology, Bayero University, Kano. 3(1): 41-49.
- Mu’azu. M.A. (2009) Evaluation of Plasticity and Particle Size Distribution characteristics of Bagasse Ash on Cement treated Lateritic soil. Retrieved from mmuazuabdulahi@yahoo.co.uk12/05/2011.
- Mustapha, A.M., Jibrin, R., Estuworo, M.M. & Alhassan, M. (2014). Stabilization of A – 6 Lateritic soil using cold reclaimed Asphalt pavement. *International Journal of Engineering & Technology*. ISSN 2049 – 3444. Vol. 4. No. 1.
- Ogunribido, T.H.T. (2011). Potentials of sugar cane show Ash for lateritic soil stabilization in Road construction. *International Journal of Science and Engineering Technology*, ISSN: 2044 – 6004, 3(5):102 – 106.
- Olugbenga, O.A. & Akinwale, A.A. (2010). Characteristics of Bamboo leaf ash stabilization of Lateritic soil in Highway Construction. *International Journal of Engineering & technology*, 2(4): 212-219.
- Omotosho, O. and Eze-Uzoamaka O.J. (2008). Optimal Stabilization of Deltaic Laterite. *Journal of the South African Institution of Civil Engineering*, 50(2): 10-17.
- Osinubi, K.J. (1998). Influence of Compaction Delay on the Properties of Cement – Stabilized Lateritic Soil. *Journal of Engineering Research*. 6(1): 13 – 25.
- Osinubi, K.J., Bafyau, V., Eberemu, A.O & Adrian, O. (2017). Bagasse Ash stabilization of lateritic soil. *Appropriate Technologies of Environmental Protection in the Developing world*. Pp. 281 – 290.
- Osinubi, K. J., Eberemu, A.O.; Bello, A.O. & Adzegah, A. (2012). Effects of Fines content on the Engineering Properties of Reconstructed Lateritic Soils in waste containment application. *Nigerian Journal of Technology*, 31(3): 277-287.
- Sharma, S.K. (2012). Principles, Practice and Design of Highway Engineering-Including Airport Pavements. Chand & Company. Ram Nagar, New Delhi.
- Singh, A. (2002). Soil Engineering in Theory and Practice. Volume 1: (Fundamentals and general principles). CBS Publishers and Distributors. New Delhi – India.
- Uche, O.A.U. (2007). The effect of donkey dung on the properties of soilcrete blocks. *Journal of Engineering and Technology*, Bayero University, Kano; Nigeria. 2(1): 45-54.