

# Modelling the Slump, Compressive Strength and Density of Concrete Containing Coconut Shell as Partial Replacement for Crushed Granite

M. Abdullahi<sup>1,\*</sup>, H. O. Aminulai<sup>1</sup>, B. Alhaji<sup>1</sup>, and M. Abubakar<sup>1</sup>  
Department of Civil Engineering, Federal University of Technology,  
Minna, Nigeria

<sup>1,\*</sup>Corresponding Author: 08167415678, [abdulapai@yahoo.com](mailto:abdulapai@yahoo.com),  
[aminulai.hammed@futminna.edu.ng](mailto:aminulai.hammed@futminna.edu.ng), [bala.alhaji@futminna.edu.ng](mailto:bala.alhaji@futminna.edu.ng),  
[mahmud1879@futminna.edu.ng](mailto:mahmud1879@futminna.edu.ng)

## Abstract

In this research, crushed coconut shell was used to partially replace crushed granite as coarse aggregate in the production of concrete. Tests were conducted on the physical properties of crushed coconut shell and crushed granite. Thirty one random mixes were generated using Mini Tab 14 statistical software package. A total of 108 cubes were cast and cured for 28 days and then crushed to determine their compressive strength. The results were used to develop empirical models for the slump, compressive strength and density of the concrete. The concrete developed in this work has slump ranging from 0 – 135 mm, compressive strength ranging from 8.94 N/mm<sup>2</sup> – 27.11 N/mm<sup>2</sup> and density ranging from 1757.04 kg/m<sup>3</sup> to 2198.52 kg/m<sup>3</sup> respectively. This implies that concrete made using coconut shell as partial replacement for crushed granite can be used for structural application such as in the construction of reinforced concrete slabs, beams, columns and foundations. Polynomial model was developed with the capability of explaining the under-laying relationship of 93.8%, 83.6% and 72.3% for slump, compressive strength and density respectively.

## Keywords

Coconut shell, slump, compressive strength, density, models

## 1. Introduction

Concrete has wide area of application in Civil Engineering and building works. Due to urbanisation, especially in developing countries like Nigeria, the use concrete product has continued to be on its increase. This has led to

increased depletion of natural resources and thereby distorting the ecological balance. This has necessitate researchers to consider waste materials in the production of concrete, since it has additional advantage of sanitising the environment (Mohammed et al. 2014a, Mohammed et al. 2014b, Mohammed et al. 2013, Mohammed et al 2011a, Mohammed et al. 2011b, Abdullahi et al. 2010, Abdullahi 2016, Oyetola and Abdullahi 2006, Abdullahi et al. 2009, Abdullahi et al. 2008). Inclusion of such unconventional materials in concrete does not easily give workable mix and requires trial mixes to come up with the desired mix compositions. A comprehensive and rational design of concrete mixes is influenced by numerous factors which depend upon the sources of materials and their properties, method of preparation, placement, compaction, curing of concrete and the requirements of a construction job. The optimum design of concrete mix involves selection of proportions of ingredients that yield concrete of the desired workability, strength and durability at minimum cost. The most important factors which influence such a mix design are the water-cement ratio (w/c), aggregate-cement ratio (TA/C) and coarse-total aggregate ratio (CA/TA) (Abbasi et al. 1987). Since these factors are inter-dependent, proper and analysis of experiments for studying their influences on the mix proportions is necessary.

Several researches have been conducted to develop new materials relying on renewable resources. These include the use of by-products and waste products such as periwinkle shell, rice husk, palm kernel, coconut shell, just to mention but a few. According to (Adewuyi and Adegoke 2008), many of these by-products are used as aggregate for the production of lightweight concrete. Due to the economic situation in developing countries like Nigeria conventional concrete materials needs substitution with more sustainable ones. Therefore, it may be beneficial to carry out research on the available local waste materials that will partially or fully substitute costly conventional materials. Numerous results have been achieved in these regards, and the subject is attracting attention due to the benefits of recycling and suitability in concrete work. Reduction in construction costs and the ability to produce lightweight structures are added advantages. In Nigeria, particularly in the south-south region and the eastern zone of Nigeria, coconut shells are available in abundance as waste. In this regard, development modelling of properties of concrete containing coconut shell as partial replacement for crushed granite is timely and justifiable.

## 2. Materials and Method

### 2.1 Materials

The materials used for this research work were sourced locally and they are as follows

- i. Natural sand (fine aggregate) obtained from River Kpakungu in Minna, Nigeria.
- ii. Crushed coconut shell and granite as coarse aggregate. The coconut shell used was obtained from Bosso in Minna, Nigeria; dried and crushed to a particular size of about 20mm.
- iii. Ordinary Portland cement, being the commonly used cement in Minna, Nigeria.
- iv. Clean water: The water used for mixing and curing was potable drinking water from tap which is suitable for concrete work (BS 3148, 1980).

### 2.2 Methods

#### 2.2.1 Aggregate Characterisation

The following tests were carried out on the aggregates: Sieve analysis, moisture content, specific gravity and bulk densities in accordance to (BS 812: part 1, 1975 and BS 812: part 109, 1990, BS 812: part 2, 1975).

#### 2.2.2 Experimental Design

Central composite design was used to select 31 candidate points for the experiment. These points include the centre point, factorial points, axial points and repetitions to allow for pure errors arising from the experimental process. The variable factors considered in the mix design are the water-cement ratio (W/C), total aggregate-cement ratio (TA/C) and coarse-total aggregate ratio (CA/TA). Absolute volume method was used for the mix design. Three mixes were also developed for model validation. In this work  $x_1$  is the water-cement ratio (W/C),  $x_2$  is the total aggregate-cement ratio (TA/C),  $x_3$  is the coarse-total aggregate ratio (CA/TA) and  $x_4$  is the percentage replacement of coconut shell with crushed granite.

#### 2.2.3 Production and Testing of Concrete

For each of the mixes three cubes (150mm x 150mm x 150mm) were cast, cured and crushed at 28 days according to (BS 1881 Part 116, 1983). Slump test was conducted before casting in accordance (BS 1881: Part 102, 1983).

### 2.2.4 Modelling

The results of the slump, compressive strength and density of the concrete were used to develop statistical models in Minitab environment. Possible models are linear, interaction, pure quadratic, full quadratic and reduced version of all the aforementioned models.

### 2.2.5 Validation

The developed models were used to compute the slump, compressive strength and density of concrete and compared with experimental data reserved for model validation.

## 3. Results and Discussion

### 3.1 Aggregate Characterisation

The specific gravity, moisture content, bulk density, fineness modulus, void ratio and porosity of sand, crushed granite and coconut shell are shown in Table 1. The specific gravity of sand and crushed granite are 2.61 and 2.74 which lies within the range for natural aggregate given as 2.5 and 3.0 (Neville, 2000). Also the specific gravity of coconut shell obtained is 1.32. This value is very low compared with that of natural aggregate. This is an indication that coconut shell is much lighter than most natural aggregate. The uncompacted bulk density of coconut shell is  $476.99\text{Kg/m}^3$  which is close to the result obtained by (Aguwa and Amadi, 2010), who reported that coconut shell has a bulk density of  $489\text{ kg/m}^3$  and can be used as a lightweight aggregate in concrete production.

The uncompacted bulk density was used in this research work because in practice, the material is not likely to be compacted before use in mixing. The porosity of coconut shell is 19.58% as shown in Table 1. This value is very high compared with most natural aggregate, which have their porosities in the range of 6 – 10%. Hence less strength is expected, because the higher the porosity of aggregate, the lower the strength and durability of concrete. The value of porosity also indicates that the coconut shell may absorb higher amount of water and cement paste during mixing compared to normal aggregates. Table 1 also shows the moisture content for the coconut shell aggregate to be 5%. This indicates that the aggregate is not too dry but at the same time will absorb some amount of water from concrete and additional water has to be added to compensate for this absorption. The same applied to the fine aggregate having a moisture content of 4.1%. However, the moisture

content for granite (crushed aggregate) is 0.5% indicating that the aggregate would only absorb little water from the concrete.

Table 1 Physical properties of constituent materials

Parameter	Sand	Crushed granite	Crushed brick
Specific gravity	2.61	2.74	3.42
Moisture content (%)	4.0	0.5	5.2
Uncompacted bulk density (kg/m <sup>3</sup> )	1468.46	1370.17	476.99
Compacted bulk density (kg/m <sup>3</sup> )	1602.54	1500.29	593.18
Fineness modulus	4.58	6.6	5.5
Void ratio	0.44	0.5	0.64
Porosity (%)	8.4	8.67	19.58

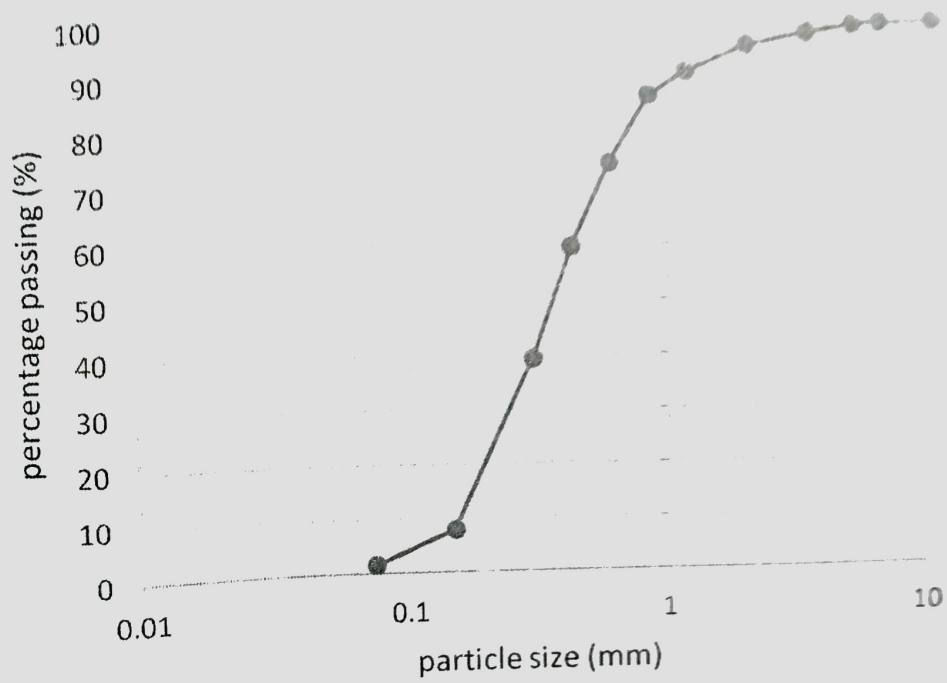


Figure 1 Sieve analysis of fine aggregate

... ..

... ..




Figure 2 Sieve analysis of crushed coconut shell

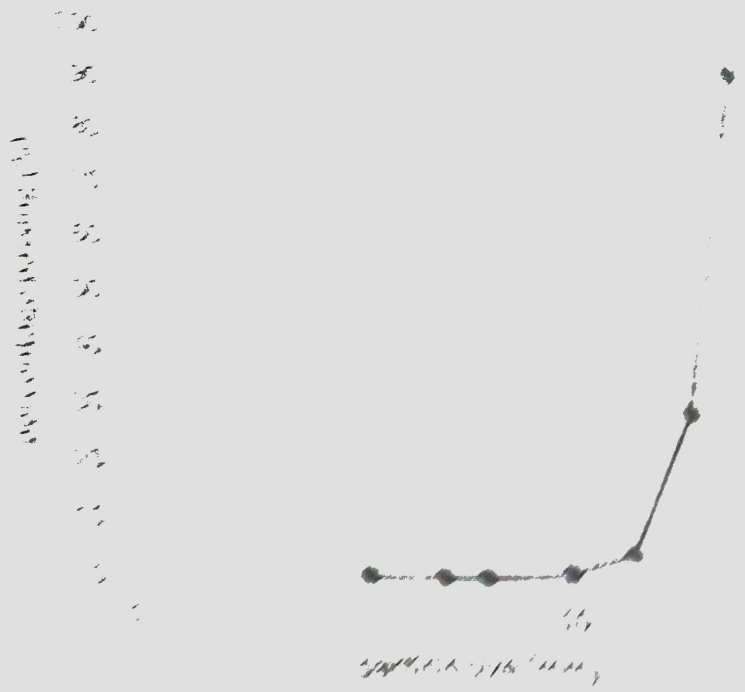


Figure 1: Graph showing the relationship between ...

### 3.2. Material Properties

The material properties, including strength and ductility, were studied in detail. The results show that the material exhibits high strength and ductility under various loading conditions. The data indicates that the material is suitable for applications requiring high performance and reliability.

### 3.3. Data Interpretation

The data obtained from the experiments was analyzed to determine the relationship between the variables. The results show that there is a strong correlation between the variables, indicating that the material properties are significantly affected by the experimental conditions. The data suggests that the material is highly sensitive to changes in the experimental parameters.

Table 2 - Slump, compressive strength and density of concrete cubes

Mix No.	X <sub>1</sub>	X <sub>2</sub>	X <sub>3</sub>	X <sub>4</sub>	Slump (mm)	Compressive strength at 28 days (N/mm <sup>2</sup> )	Density (kg/m <sup>3</sup> )
1	0.36	0.60	4.00	0.24	0	10.05	1979.3
2	0.40	0.65	3.00	0.36	20	17.2	1961.3
3	0.50	0.67	4.00	0.24	5	15.91	2038.5
4	0.40	0.55	3.00	0.36	10	15.78	1997
5	0.40	0.65	5.00	0.12	0	11.29	2094.8
6	0.50	0.60	5.41	0.24	0	6.28	1970.4
7	0.60	0.65	5.00	0.12	20	12.65	2154.1
8	0.60	0.55	5.00	0.36	10	9.33	1982.22
9	0.40	0.55	3.00	0.12	20	20.88	2198.52
10	0.60	0.65	3.00	0.36	120	8.95	1896.3
11	0.50	0.60	4.00	0.41	0	11.61	1917.04
12	0.50	0.60	4.00	0.24	10	19.7	2091.85
13	0.60	0.55	5.00	0.12	10	15.2	2106.07
14	0.50	0.60	4.00	0.24	0	17.17	1985.19
15	0.60	0.65	5.00	0.36	0	10.8	1920
16	0.40	0.55	5.00	0.12	0	8.79	1982.19
17	0.50	0.60	4.00	0.24	10	16.71	1991.11
18	0.50	0.53	4.00	0.24	10	18.03	2071.11
19	0.40	0.65	5.00	0.36	0	3.51	1757.04
20	0.60	0.55	3.00	0.12	125	15.35	2080
21	0.50	0.60	4.00	0.24	5	13.75	1914.07
22	0.50	0.60	4.00	0.24	15	12.74	2071.11
23	0.40	0.65	3.00	0.12	20	27.11	2225.19
24	0.50	0.60	2.59	0.24	70	18.8	2044.44
25	0.60	0.65	3.00	0.12	135	16.71	2109.63
26	0.50	0.60	4.00	0.07	25	23.63	2198.52
27	0.60	0.55	3.00	0.36	90	11.64	1994.07
28	0.50	0.60	4.00	0.24	20	19.64	2145.19
29	0.50	0.60	4.00	0.24	10	18.4	2005.19
30	0.40	0.55	5.00	0.36	0	4.3	1851.85
31	0.64	0.60	4.00	0.24	60	11.54	2035.55
32	0.5	0.55	3.50	0.24	10	12.8	2133.33
33	0.45	0.60	4.50	0.30	0	4.84	1917.04
34	0.6	0.65	5.00	0.18	10	11.47	2162.96

### 3.3.1 Slump model

A reduced full quadratic model was found to be most appropriate for the slump model. Its residual values were reasonable when compared with other models generated for slump. The slump model generated is as follows:



$$Y_1 = 79.46 - 71.87X_1 - 29.55X_3 + 1236.85X_1^2 + 14.14X_3^2 - 225.86X_1X_3$$

$$R_S Q = 94.5\% , R_S Q(ADJ) = 93.5\%$$

### 3.3.2 Compressive strength model

A full quadratic model was found to be most adequate for explaining the experimental data for compressive strength. The model is as follows:

$$Y_2 = -17.75 + 201.8X_1 - 5.58X_2 - 0.21X_3 - 47.59X_4 - 248.56X_1^2 + 124.82X_2^2 - 1.71X_3^2 + 69.79X_4^2 - 151.63X_1X_2 + 30.95X_1X_3 - 50.7X_1X_4 - 10.17X_2X_3 - 82.81X_2X_4 + 2.71X_3X_4$$

$$R_S Q = 85.6\% , R_S Q(ADJ) = 75\%$$

### 3.3.3 Density model

A full quadratic model was also considered appropriate for the density model. The model is as follows:

$$Y_3 = 4615.71 + 235.91X_1 - 6682.83X_2 - 283.89X_3 + 1857.5X_4 - 1683.64X_1^2 + 6136.89X_2^2 - 14.76X_3^2 + 293.84X_4^2 - 537.89X_1X_2 + 519.29X_1X_3 + 1336.17X_1X_4 + 196.83X_2X_3 - 5536.19X_2X_4 - 46.72X_3X_4$$

$$Rsq = 87.1\% , Rsq(adj) = 77.6\%$$

### 3.3.4 Response Surface Plot

The response surface plot for slump, compressive strength and density models are shown in Figures 4, 5, and 6 respectively.





Figure 4: Response Surface Plot for Slump

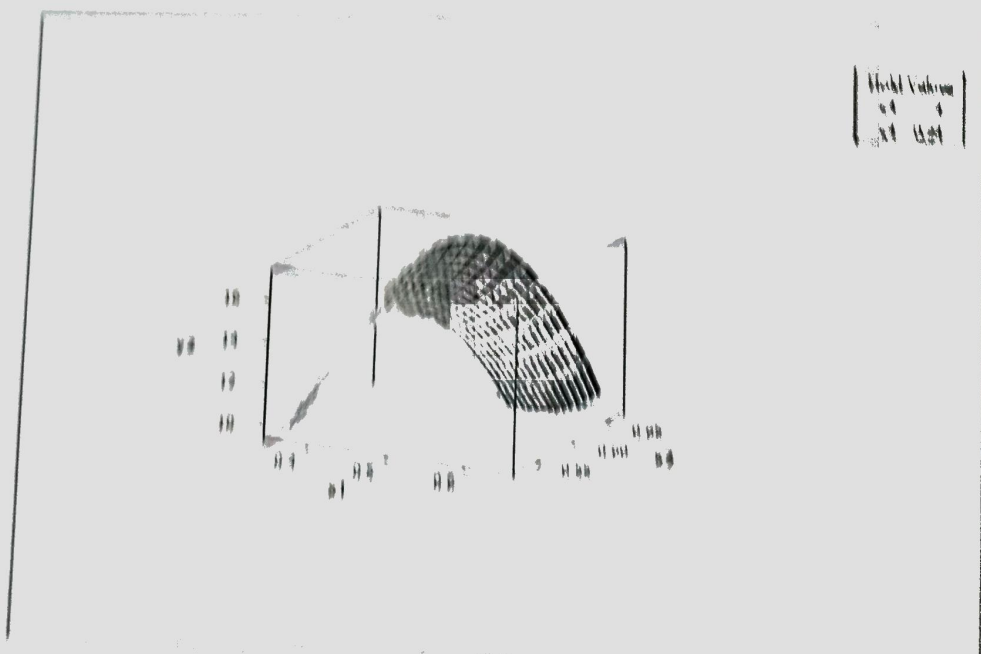

(A)

Figure 5: Response surface plot for compressive strength

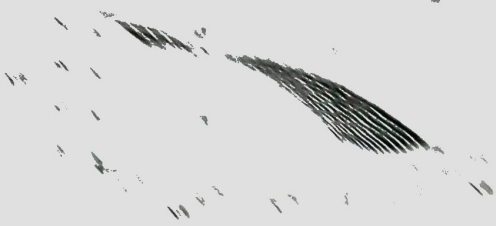


Figure 1: A 3D surface plot showing a curved, elongated shape, likely representing a component of a mechanical part.



Figure 2: A 3D surface plot showing a curved, elongated shape, likely representing a component of a mechanical part.



(b)

Figure 6 Response Surface Plot for Density

### 3.4 Model validation

To validate the adequacy of the fitted models, the mix compositions in the three mixes employed for this purpose were used to compute the slump, compressive strength and density using the models. The experimental and model data are shown in Table 3. The result shows that the polynomial models are capable of computing the properties of the concrete.

Table 3: Comparison of experimental data with model data

SNo	Factors				Experimental Data			Model Data		
	X1	X2	X3	X4	Y1 (mm)	Y2 (N/mm <sup>2</sup> )	Y3 (kg m <sup>3</sup> )	Y1 (mm)	Y2 (N/mm <sup>2</sup> )	Y3 (kg m <sup>3</sup> )
1	0.50	0.33	3.50	0.24	10	12.80	2111.1	30	18.00	2068.14
2	0.45	0.60	4.50	0.30	0	4.84	1917	0	11.01	1941.00
3	0.60	0.63	5.0	0.18	10	11.47	2163	10	11.95	2091.43

## 1. Conclusion

From the results obtained on the tests conducted on the concrete developed using crushed coconut shell as partial replacement for crushed granite, the following conclusions are hereby made:

- (i) The specific gravity, uncompact bulk density, compacted bulk density for coconut shell were found to be 1.32, 476.99 kg/m<sup>3</sup> and 593.18 kg/m<sup>3</sup> respectively.
- (ii) The slump, compressive strength and density of concrete containing crushed coconut shell ranges from 0 mm to 135 mm, 3.51 N/mm<sup>2</sup> to 27.11 N/mm<sup>2</sup> and 1757.04 kg/m<sup>3</sup> to 2198.52 kg/m<sup>3</sup> respectively.
- (iii) Polynomial models were obtained for slump, compressive strength and density for concrete containing crushed coconut shell as partial replacement for crushed granite with predictive capabilities of 93.5%, 75% and 77.6% respectively.

## References

- Abbasi A. P., Ahmad M. and Wasim M. (1987). Optimization of concrete mix proportioning using reduced factorial technique. American Concrete Institute. ACI Material Journal.
- Abdullahi M., Al Mattarneh, H.M.A. and Mohammed B.S. (2010) Characterisation of Palm Oil Clinker Aggregate. International Journal of Applied Engineering Research. Research Indian Publications, India, 5(16), 3877-3882.
- Abdullahi M., Al Mattarneh H.M.A., and Mohammed, B.S. (2009). Mixture Proportioning Methodology for Palm Oil Clinker Concrete. Proceeding of 10<sup>th</sup> International Conference on Concrete Engineering and Technology (ICCET-09). High Performance Concrete, Special Concrete, Recycled Waste and Bio Concrete. Held at Grand Season Hotel, Kuala Lumpur, Malaysia. 3-4 March 2009 (In CD Rom).

Abdullahi M., Al-Mattarneh H.M.A., Hassan A.H. Abu., Hassan Md.H., and Mohammed. B.S. (2008). Trial Mix Design Methodology for Palm Oil Clinker (POC) Concrete. Proceeding of International Conference on Construction and Building Technology (ICCBT2008): Emerging Technology in Construction Materials. Held at Grand Season Hotel, Kuala Lumpur, Malaysia. 16-20 June 2008, 507 – 516.

Abdullahi M. (2006) Characteristics of Wood Ash/OPC Concrete. Leonardo Electronic Journal of Practices and Technologies, Romania. 8(1), 9-16.

Adewuyi A. P. and Adegoke T. (2008). Exploratory study of Coconut/Periwinkle shell in concrete works. ARPN Journal of Engineering and Applied Science, 2(3), p.12.

Aguwa, J.I. and Amadi, A.A. (2010). Performance of coconut shell as coarse aggregate for production of lightweight concrete, Global Journal of Engineering and Technology, 3(4): 695- 701

BS 812: part 109 (1990). Method of determination of moisture content. British Standard Institution, Her Majesty Stationary office London.

BS 812: part 1 (1975). Method for determination of particle size and shape. British Standard Institution, Her Majesty Stationary office London.

BS 812: part 2 (1975). Methods for determination of physical properties of aggregate. British Standard Institution, Her Majesty Stationary office London.

BS 882 (1992). Specification for aggregates from natural sources for concrete, British Standard Institution, Her Majesty Stationary office London.

BS 1881: Part 102 (1983). Method for determination of slump of fresh concrete. British Standard Institution, Her Majesty Stationary office London.

BS 1881 Part 116 (1983). Method for determining compressive strength of concrete cubes. British Standard Institution, Her Majesty Stationary office London.

1945-1946

1. The first part of the report deals with the general situation in the country.

2. The second part of the report deals with the economic situation in the country.

3. The third part of the report deals with the social situation in the country.

4. The fourth part of the report deals with the political situation in the country.

5. The fifth part of the report deals with the cultural situation in the country.

6. The sixth part of the report deals with the international situation in the country.

7. The seventh part of the report deals with the future prospects of the country.

8. The eighth part of the report deals with the conclusions of the report.